

# Aggregate Optimization Chart

MIX ID'S: DDD0K7E7 and DDD0K7E9

Production Gradation Report

**PLANT #:** **P-103**

Sample Date: 7/24/17

Concrete Grade: **DM**

Contractor: \_\_\_\_\_

Dates Test Represents: 7/24/2017 to 7/30/2017

MDOT No.: \_\_\_\_\_

Agg. Class	Pit #	Source	Weight (SSD)	ft <sup>3</sup>	Specific Gravity	% Contribution
6AA	58-003	Stoneco	1550	9.23	2.69	51.8
26A	58-003	Stoneco	200	1.19	2.69	6.7
2NS	81-93	Burmeister	1240	7.53	2.64	41.5
<b>Total Wt</b>			<b>2990</b>	<b>17.95</b>		<b>100.0</b>

<----- Verify this number is 100%

Sieve	6AA	26A	2NS	Cumulative % Passing	% Retained	Cumulative % Retained
2"	100.0	100.0	100.0	100.0	0.0	0.0
1.5"	100.0	100.0	100.0	100.0	0.0	0.0
1"	99.5	100.0	100.0	99.7	0.3	0.3
3/4"	82.3	100.0	100.0	90.8	8.9	9.2
1/2"	44.4	99.2	100.0	71.1	19.7	28.9
3/8"	24.7	84.6	100.0	59.9	11.2	40.1
#4	2.3	25.5	97.7	43.4	16.5	56.6
#8	1.1	4.9	83.0	35.3	8.1	64.7
#16	0.5	2.1	67.0	28.2	7.1	71.8
#30	0.4	1.7	48.8	20.6	7.6	79.4
#50	0.3	1.5	24.5	10.4	10.1	89.6
#100	0.2	1.4	5.5	2.5	7.9	97.5
LBW	0.5	1.3	1.7	1.1	1.4	98.9




**Superior Materials, LLC**  
 30701 W. 10 Mile Rd.  
 Suite 500  
 Farmington Hills, MI 48336

\*Maximum % Retained must be above the 3/8" sieve.  
 \*Any two adjacent sieves must equal 10% except max., nom. max., #100 and #200 sieves.  
 \*% Retained must be at least 4% for each sieve except max., nom. max., #100 and #200 sieves.  
 \*% Retained must be at least 8% for the 1" sieve when a 2" max. size (nom. Max. 1.5") aggregate is used.

Production Gradation  Batch Plant Gradations  Aggregate Supplier Gradations

<b>Coarseness Factor:</b>	<b>62</b>	<b>Workability Factor:</b>	<b>35</b>
---------------------------	-----------	----------------------------	-----------

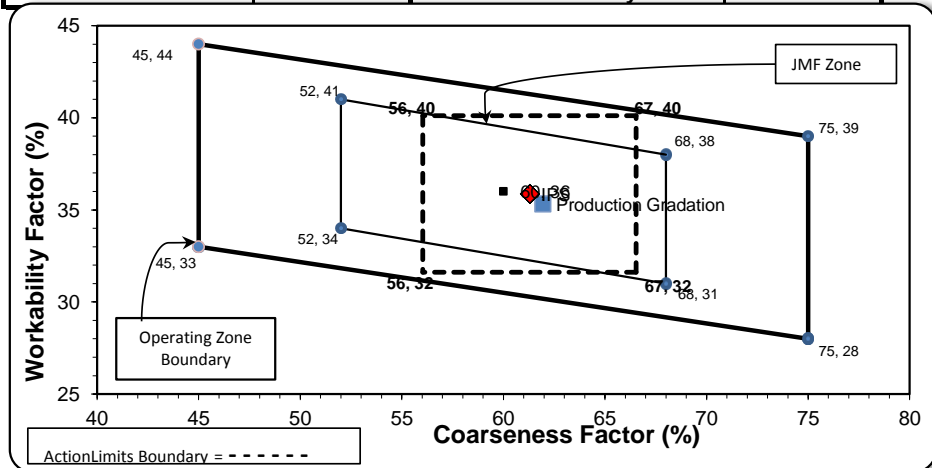

Initial Production Sample (IPS)

<b>Coarseness Factor:</b>	<b>61</b>		
<b>Workability Factor:</b>	<b>36</b>		
Sieve	Cumulative % Passing	% Retained	Cumulative % Retained
2"	100.0	0.0	0.0
1.5"	100.0	0.0	0.0
1"	99.3	0.7	0.7
3/4"	89.2	10.1	10.8
1/2"	70.7	18.5	29.3
3/8"	60.7	10.0	39.3
#4	44.4	16.3	55.6
#8	35.9	8.5	64.1
#16	27.3	8.6	72.7
#30	19.1	8.2	80.9
#50	7.4	11.7	92.6
#100	1.9	5.6	98.1
LBW	0.7	1.2	99.3

PREPARED BY:  
 SM, LLC Technical Service

Approved BY:

# Aggregate Optimization Chart

MIX ID'S: DDD0K7E7 and DDD0K7E9

Production Gradation Report

**PLANT #:** **P-32**

Sample Date: 7/24/17

Concrete Grade: **DM**

Contractor: \_\_\_\_\_

Dates Test Represents: 7/24/2017 to 7/30/2017

MDOT No.: \_\_\_\_\_

Agg. Class	Pit #	Source	Weight (SSD)	ft <sup>3</sup>	Specific Gravity	% Contribution
6AA	71-47	Presque Isle	1500	9.17	2.62	50.8
26A	71-47	Presque Isle	250	1.53	2.62	8.5
2NS	95-13	Smelter Bay	1200	7.26	2.65	40.7
<b>Total Wt</b>			<b>2950</b>	<b>17.96</b>		<b>100.0</b>

<----- Verify this number is 100%

Sieve	6AA	26A	2NS	Cumulative % Passing	% Retained	Cumulative % Retained
2"	100.0	100.0	100.0	100.0	0.0	0.0
1.5"	100.0	100.0	100.0	100.0	0.0	0.0
1"	100.0	100.0	100.0	100.0	0.0	0.0
3/4"	82.0	100.0	100.0	90.8	9.2	9.2
1/2"	37.0	98.6	100.0	67.8	23.0	32.2
3/8"	20.0	87.1	100.0	58.2	9.6	41.8
#4	3.8	13.5	95.2	41.8	16.4	58.2
#8	2.1	2.7	85.0	35.9	5.9	64.1
#16	1.8	1.8	70.9	29.9	6.0	70.1
#30	1.7	1.6	50.5	21.5	8.4	78.5
#50	1.6	1.5	23.6	10.5	11.0	89.5
#100	1.4	1.5	7.1	3.7	6.8	96.3
LBW	1.2	1.3	1.8	1.5	2.3	98.5


\*Maximum % Retained must be above the 3/8" sieve.  
 \*Any two adjacent sieves must equal 10% except max., nom. max., #100 and #200 sieves.  
 \*% Retained must be at least 4% for each sieve except max., nom. max., #100 and #200 sieves.  
 \*% Retained must be at least 8% for the 1" sieve when a 2" max. size (nom. Max. 1.5") aggregate is used.



**Superior Materials, LLC**  
 30701 W. 10 Mile Rd.  
 Suite 500  
 Farmington Hills, MI 48336

Production Gradation  Batch Plant Gradations  Aggregate Supplier Gradations

**Coarseness Factor:** **65**      **Workability Factor:** **36**

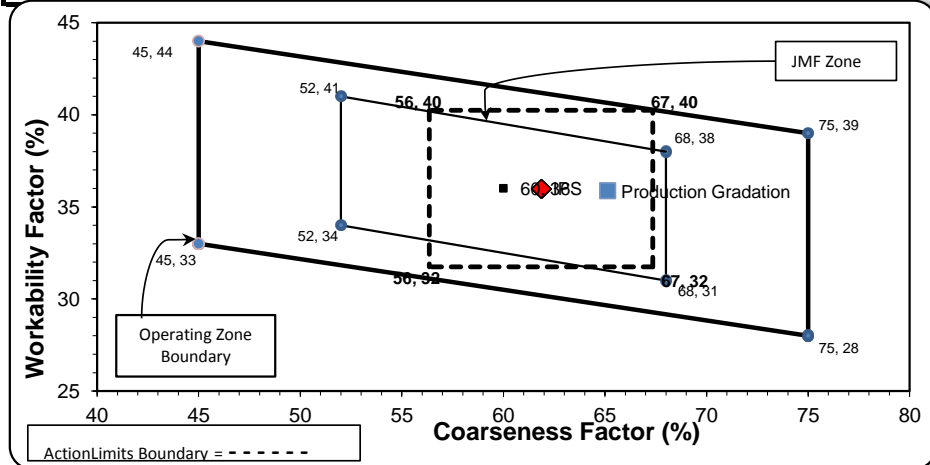

Initial Production Sample (IPS)

Coarseness Factor:		62	
Workability Factor:		36	
Sieve	Cumulative % Passing	% Retained	Cumulative % Retained
2"	100.0	0.0	0.0
1.5"	100.0	0.0	0.0
1"	100.0	0.0	0.0
3/4"	95.0	5.0	5.0
1/2"	72.3	22.8	27.7
3/8"	60.4	11.8	39.6
#4	42.6	17.8	57.4
#8	36.0	6.6	64.0
#16	29.5	6.5	70.5
#30	20.3	9.2	79.7
#50	9.5	10.8	90.5
#100	3.4	6.1	96.6
LBW	1.3	2.1	98.7

PREPARED BY:  
 SM, LLC Technical Service

Approved By:

# Aggregate Optimization Chart

MIX ID'S: DDD0K7E7 and DDD0K7E9

Production Gradation Report

**PLANT #:** **P-36**

Sample Date: 7/24/17

Concrete Grade: **DM**

Contractor: \_\_\_\_\_

Dates Test Represents: 7/24/2017 to 7/30/2017

MDOT No.: \_\_\_\_\_

Agg. Class	Pit #	Source	Weight (SSD)	ft <sup>3</sup>	Specific Gravity	% Contribution
6AA	58-003	Stoneco	1580	9.41	2.69	52.8
26A	71-47	Presque Isle	200	1.22	2.62	6.7
2NS	63-92	AA Grange Hall	1210	7.32	2.65	40.5
<b>Total Wt</b>			<b>2990</b>	<b>17.95</b>		<b>100.0</b>

<----- Verify this number is 100%

Sieve	6AA	26A	2NS	Cumulative % Passing	% Retained	Cumulative % Retained
2"	100.0	100.0	100.0	100.0	0.0	0.0
1.5"	100.0	100.0	100.0	100.0	0.0	0.0
1"	99.5	100.0	100.0	99.7	0.3	0.3
3/4"	82.3	100.0	100.0	90.6	9.1	9.4
1/2"	44.4	98.6	100.0	70.5	20.1	29.5
3/8"	24.7	87.1	100.0	59.3	11.2	40.7
#4	2.3	13.5	98.5	42.0	17.4	58.0
#8	1.1	2.7	87.9	36.3	5.6	63.7
#16	0.5	1.8	71.2	29.2	7.1	70.8
#30	0.4	1.6	49.7	20.4	8.8	79.6
#50	0.3	1.5	18.4	7.7	12.7	92.3
#100	0.2	1.5	2.6	1.3	6.4	98.7
LBW	0.5	1.3	0.3	0.5	0.8	99.5


\*Maximum % Retained must be above the 3/8" sieve.  
 \*Any two adjacent sieves must equal 10% except max., nom. max., #100 and #200 sieves.  
 \*% Retained must be at least 4% for each sieve except max., nom. max., #100 and #200 sieves.  
 \*% Retained must be at least 8% for the 1" sieve when a 2" max. size (nom. Max. 1.5") aggregate is used.



**Superior Materials, LLC**  
 30701 W. 10 Mile Rd.  
 Suite 500  
 Farmington Hills, MI 48336

Production Gradation  Batch Plant Gradations  Aggregate Supplier Gradations

**Coarseness Factor: 64**      **Workability Factor: 36**

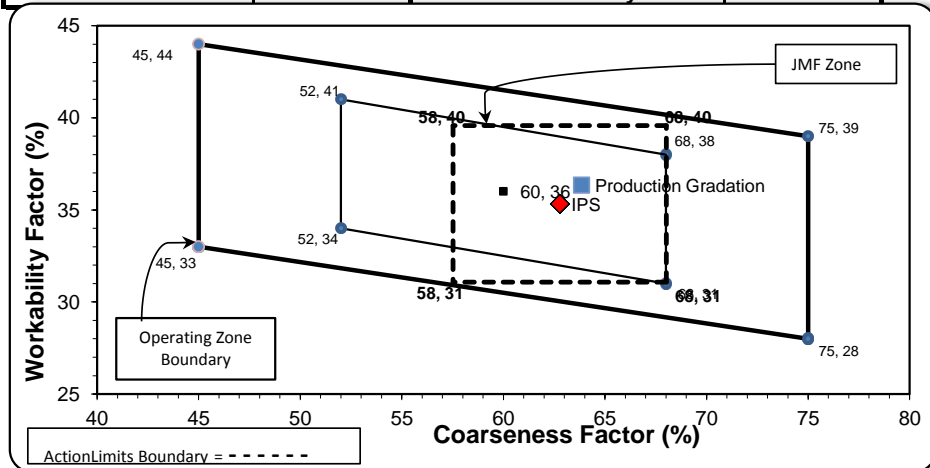

Initial Production Sample (IPS)

Coarseness Factor: 63		Workability Factor: 35	
Sieve	Cumulative % Passing	% Retained	Cumulative % Retained
2"	100.0	0.0	0.0
1.5"	100.0	0.0	0.0
1"	99.9	0.1	0.1
3/4"	89.1	10.8	10.9
1/2"	71.3	17.8	28.7
3/8"	59.4	11.9	40.6
#4	42.6	16.8	57.4
#8	35.3	7.3	64.7
#16	28.5	6.8	71.5
#30	20.9	7.6	79.1
#50	9.0	12.0	91.0
#100	1.7	7.3	98.3
LBW	0.7	1.0	99.3

PREPARED BY:  
 SM, LLC Technical Service

Approved By:

# Aggregate Optimization Chart

MIX ID'S: DDD0K7E7 and DDD0K7E9

Production Gradation Report

**PLANT #:** **P-38**

Sample Date: 7/24/17

Concrete Grade: **DM**

Contractor: \_\_\_\_\_

Dates Test Represents: 7/24/2017 to 7/30/2017

MDOT No.: \_\_\_\_\_

Agg. Class	Pit #	Source	Weight (SSD)	ft <sup>3</sup>	Specific Gravity	% Contribution
6AA	58-003	Stoneco	1550	9.23	2.69	51.8
26A	58-003	Stoneco	200	1.19	2.69	6.7
2NS	81-93	Burmeister	1240	7.53	2.64	41.5
<b>Total Wt</b>			<b>2990</b>	<b>17.95</b>		<b>100.0</b>

<----- Verify this number is 100%




**Superior Materials, LLC**  
 30701 W. 10 Mile Rd.  
 Suite 500  
 Farmington Hills, MI 48336

Sieve	6AA	26A	2NS	Cumulative % Passing	% Retained	Cumulative % Retained
2"	100.0	100.0	100.0	100.0	0.0	0.0
1.5"	100.0	100.0	100.0	100.0	0.0	0.0
1"	99.5	100.0	100.0	99.7	0.3	0.3
3/4"	82.3	100.0	100.0	90.8	8.9	9.2
1/2"	44.4	99.2	100.0	71.1	19.7	28.9
3/8"	24.7	84.6	100.0	59.9	11.2	40.1
#4	2.3	25.5	97.7	43.4	16.5	56.6
#8	1.1	4.9	83.0	35.3	8.1	64.7
#16	0.5	2.1	67.0	28.2	7.1	71.8
#30	0.4	1.7	48.8	20.6	7.6	79.4
#50	0.3	1.5	24.5	10.4	10.1	89.6
#100	0.2	1.4	5.5	2.5	7.9	97.5
LBW	0.5	1.3	1.7	1.1	1.4	98.9

\*Maximum % Retained must be above the 3/8" sieve.  
 \*Any two adjacent sieves must equal 10% except max., nom. max., #100 and #200 sieves.  
 \*% Retained must be at least 4% for each sieve except max., nom. max., #100 and #200 sieves.  
 \*% Retained must be at least 8% for the 1" sieve when a 2" max. size (nom. Max. 1.5") aggregate is used.

Production Gradation  Batch Plant Gradations  Aggregate Supplier Gradations

<b>Coarseness Factor:</b>	<b>62</b>	<b>Workability Factor:</b>	<b>35</b>
---------------------------	-----------	----------------------------	-----------

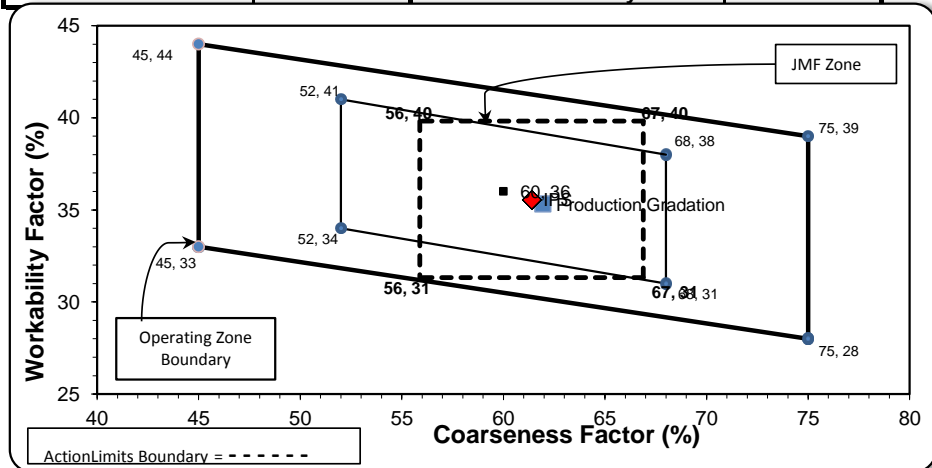

Initial Production Sample (IPS)

<b>Coarseness Factor:</b>	<b>61</b>		
<b>Workability Factor:</b>	<b>36</b>		
Sieve	Cumulative % Passing	% Retained	Cumulative % Retained
2"	100.0	0.0	0.0
1.5"	100.0	0.0	0.0
1"	99.3	0.7	0.7
3/4"	89.1	10.2	10.9
1/2"	70.5	18.6	29.5
3/8"	60.5	10.0	39.5
#4	44.1	16.4	55.9
#8	35.6	8.5	64.4
#16	27.7	7.9	72.3
#30	20.6	7.1	79.4
#50	8.7	11.8	91.3
#100	1.6	7.1	98.4
LBW	1.1	0.6	98.9

PREPARED BY:  
 SM, LLC Technical Service

Approved By: